

TEST REPORT

2024EP0609

DATE OF RECEPTION

Date Format: dd/MM/yyyy 01/02/2024

DATE TESTS

Starting: 06/02/2024 Ending: 22/02/2024 **APPLICANT**

PORTWEST UC
WESTPORT BUSINESS AND TECHNOLOGY PARK
WESTPORT (CO MAYO)
Ireland

Att. Celia Cunney

IDENTIFICATION AND DESCRIPTION OF SAMPLES

Reference by AITEX	Reference by customer	AITEX sample description
2024EP0609-S01	UAF73	Coverall

TESTS CARRIED OUT

- PRE-TREATMENT FOR DOMESTIC WASHING AND DRYING PROCEDURES FOR TEXTILE TESTING.
- PROTECTIVE CLOTHING AGAINST HEAT AND FLAME TEST METHOD FOR COMPLETE GARMENTS PREDICTION FOR BURN INJURY USING AN INSTRUMENTED MANIKIN.





DESCRIPTION OF SAMPLES

Reference by AITEX: 2024EP0609-S01

Reference by customer:

UAF73



AITEX Subsamples

2024EP0609-S01_P1

After 1 wash cycle / Coverall

RESULTS

SAMPLE DESCRIPTION

REFERENCE:

UAF73

SAMPLE TYPE:

Coverall

BODY PARTS COVERED BY THE GARMENT:

Torso, neck, and the upper and lower extremities, apart from the hands and feet.

SIZE:

42

GARMENT LAYERS:

Lover 1	Navy blue woven fabric, 93% para-aramid, 5% meta-aramid, 2% antistatic,
Layer 1	150 g/m ² , according to the information supplied by the customer.

PARTS OF THE GARMENT:

Collar	Double fabric layer 1.
Front	Four pieces of fabric layer 1.
Back	Three piece of fabric layer 1.
Sleeves	Long sleeves.
Closure system	Zipper with flap closed by snap buttons.
Collar closure system	No.
Cuff closure system	Self-fastening tape.
Deflective trim	One around each leg and arm and one at each
Reflective trim	shoulder.
	Patch pocket with flap and snap buttons (seat)+
Pockets	French pockets + Patch pocket with flap and zipper
	(chest)
Belt loops	No.
Legs	Longs.
Waistband adjustment system	Elastic tape.
Bottom	No.
Others	Sewn logos.

RESULTS

PRE-TREATMENT FOR DOMESTIC WASHING AND DRYING PROCEDURES FOR TEXTILE TESTING

Standard

EN ISO 6330:2021

Test date

Start date 06/02/2024 **End date** 06/02/2024

Washing procedure

6N

Washing temperature

60°C

Washing cycles

1

Dryer type

James Heal

Drying procedure

F (type A1 tumble drying)

Drying temperature

60°C

Washing powder

Reference detergent 3

Reference

2024EP0609-S01

Units	Dry mass of the samples(Kg)	Counterweight mass(Kg)	Counterweight type	Equipment
1	1.5	0.5	Type III	WASCATOR
2	1.5	0.5	Type III	WASCATOR

The test was carried out at laboratory located at Carretera Banyeres s/n - 03802 Alcoi, Alicante

Reference	Description	
2024EP0609-S01	UAF73	

RESULTS

PROTECTIVE CLOTHING AGAINST HEAT AND FLAME – TEST METHOD FOR COMPLETE GARMENTS – PREDICTION FOR BURN INJURY USING AN INSTRUMENTED MANIKIN

THERMO TEX TEST

Standard

ISO 13506-1:2017

Test type

End-use garment specification

Testing date

22/02/2024 - 22/02/2024

Reference

2024EP0609-S01_P1

Underwear and accessories

Shirt underwear Long sleeves shirt 100% cotton, 140 g/m² **Trousers underwear** Long trousers 100% cotton, 140 g/m²

Holes and/or cuts

Top back of the T-shirt undergarment

Apparatus

Instrumented Manikin

Test uncertainty

± 7% of the measurand's value, for a coverage value of K=2 (95%)

Conditioning

24h, in indoor ambient conditions at 20 ± 5 °C and 65 ± 5 %HR

Pre-treatment

1 cycles of washing at 60°C, according to standard EN ISO 6330:2021, method 6N and drying process F

Pre-treatment starting date

06/02/2024

Pre-treatment ending date

06/02/2024

Observation or deviation of the standard

Exposure conditions:

Total number of burners: 12 in two tiers of six surrounding the manikin. The lower set of six burners are pointed at the legs and lower body of the manikin whilst the upper set of six burners are pointed at the upper body and head


Nominal exposure heat flux density level

84 $kW / m^2 \pm 5\%$

Level of the exposure	Before the test	After the test	
Average of heat flux density	86.22 kW/m ²	83.68 kW/m ²	kW/m²
Standard deviation of the average of heat flux density	17.29 kW/m²	16.71 kW/m²	-

Distribution of burners surrounding the mannequin:

Number of burners: 12

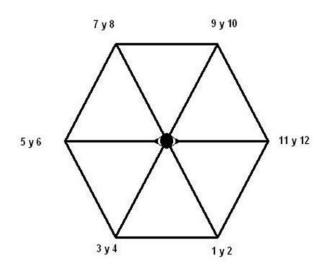

Sample nº 1 Ref.- 2024EP0609-S01_P1

Duration of the exposure

Duration of the data acquisition

Temperature of the exposure

chamber before the test

4 s 120 s 20,1 °C

Total Surface Area
Total Clothed Surface Area
Total transferred energy


1,80 m² 1,68 m² 202,72 kJ


Predicted total burn injury of the manikin

For this test, therefore, hands and feet are not included in the calculations.

First-degree burn injury area (%)	2nd degree burn injury area (%)	3rd-degree burn injury area (%)	Predicted total area of burn injury (2nd and 3rd degree) (%)
0,8	23,3	6,7	30,0



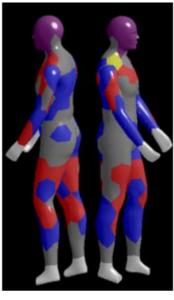



Sample nº 1 Ref.- 2024EP0609-S01_P1

Property	Measurement	Sample 1	Remark
Afterflame time	Video	1,2 s.	
Hole formation	Visual	Yes	
Melting	Visual	Yes	Labels
Embrittlement	Visual	Yes	
Smoke	Visual	Yes	
Dripping	Visual	No	
Shrinkage	Visual	Yes	
Functioning of garment accessories	Visual	Correct	

Heat Flux, Standard Deviation, Transferred Energy and Energy Transmission Factor per Body part

Sensor/temp.	Sample 1
Left arm – Heat Flux (kW/m²)	1,0
Left arm – Stdev (kW/m²)	0,2
Left arm – Transferred energy (kJ)	22,3
Left arm – Energy transmission factor	0,4
Right arm – Heat Flux (kW/m²)	1,1
Right arm – Stdev (kW/m²)	0,2
Right arm – Transferred energy (kJ)	22,9
Right arm – Energy transmission factor	0,4
Left Leg – Heat Flux (kW/m²)	1,0
Left Leg – Stdev (kW/m²)	0,3
Left Leg – Transferred energy (kJ)	45,6
Left Leg – Energy transmission factor	0,4
Right Leg – Heat Flux (kW/m²)	0,9
Right Leg – Stdev (kW/m²)	0,4
Right Leg – Transferred energy (kJ)	44,5
Right Leg – Energy transmission factor	0,3
Chest and abdomen - Heat Flux (kW/m²)	0,7
Chest and abdomen - Stdev (kW/m²)	0,3
Chest and abdomen - Transferred energy (kJ)	32,2
Chest and abdomen – Energy transmission factor	0,3
Back – Heat Flux (kW/m²)	0,8
Back – Stdev (kW/m²)	0,2
Back – Transferred energy (kJ)	29,9
Back – Energy transmission factor	0,3
Total energy transferred (kJ)	202,7
Total energy transmission factor	0,3


Sample before test nº 1 Ref.- 2024EP0609-S01_P1





Sample nº 1 Ref.- 2024EP0609-S01_P1

Clothed Burn Injury Over Time

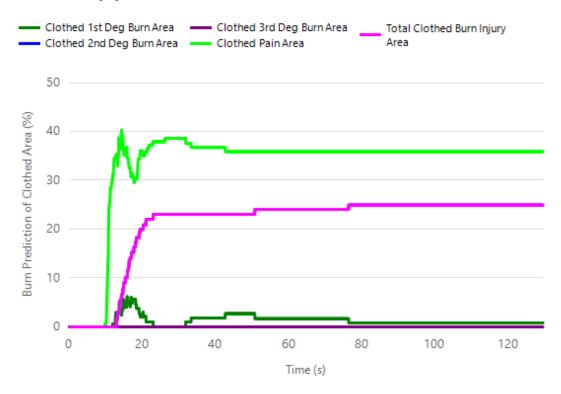

Sample after test nº 1 Ref.- 2024EP0609-S01_P1









Sample nº 2 Ref.- 2024EP0609-S01_P1

Duration of the exposure

Duration of the data acquisition

Temperature of the exposure

chamber before the test

120 s 18,6 °C

4 s

Total Surface Area
Total Clothed Surface Area
Total transferred energy


1,80 m² 1,68 m² 202,72 kJ


Predicted total burn injury of the manikin

For this test, therefore, hands and feet are not included in the calculations.

First-degree burn injury area (%)	2nd degree burn injury area (%)	3rd-degree burn injury area (%)	Predicted total area of burn injury (2nd and 3rd degree) (%)
5,4	23,7	7,3	31,1



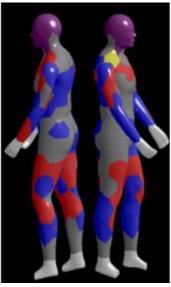



Sample nº 2 Ref.- 2024EP0609-S01_P1

Property	Measurement	Sample 2	Remark
Afterflame time	Video	1,1 s.	
Hole formation	Visual	No	
Melting	Visual	Yes	Labels
Embrittlement	Visual	Yes	
Smoke	Visual	Yes	
Dripping	Visual	No	
Shrinkage	Visual	Yes	
Functioning of garment accessories	Visual	Correct	

Heat Flux, Standard Deviation, Transferred Energy and Energy Transmission Factor per Body part

Sensor/temp.	Sample 2
Left arm – Heat Flux (kW/m²)	1,1
Left arm – Stdev (kW/m²)	0,3
Left arm – Transferred energy (kJ)	23,6
Left arm – Energy transmission factor	0,4
Right arm – Heat Flux (kW/m²)	1,1
Right arm – Stdev (kW/m²)	0,3
Right arm – Transferred energy (kJ)	23,7
Right arm – Energy transmission factor	0,4
Left Leg – Heat Flux (kW/m²)	1,0
Left Leg – Stdev (kW/m²)	0,4
Left Leg – Transferred energy (kJ)	46,8
Left Leg – Energy transmission factor	0,4
Right Leg – Heat Flux (kW/m²)	0,9
Right Leg – Stdev (kW/m²)	0,3
Right Leg – Transferred energy (kJ)	43,2
Right Leg – Energy transmission factor	0,3
Chest and abdomen - Heat Flux (kW/m²)	0,7
Chest and abdomen - Stdev (kW/m²)	0,3
Chest and abdomen - Transferred energy (kJ)	32,9
Chest and abdomen – Energy transmission factor	0,3
Back – Heat Flux (kW/m²)	0,8
Back – Stdev (kW/m²)	0,2
Back – Transferred energy (kJ)	31,3
Back – Energy transmission factor	0,3
Total energy transferred (kJ)	206,8
Total energy transmission factor	0,3




Sample before test nº 2 Ref.- 2024EP0609-S01_P1





Sample nº 2 Ref.- 2024EP0609-S01_P1

Clothed Burn Injury Over Time

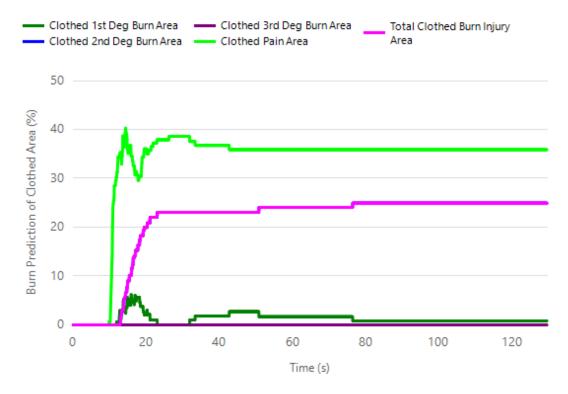

Sample after test nº 2 Ref.- 2024EP0609-S01_P1









Sample nº 3 Ref.- 2024EP0609-S01_P1

Duration of the exposure

Duration of the data acquisition

Temperature of the exposure

chamber before the test

120 s 18,9 °C

4 s

Total Surface Area
Total Clothed Surface Area
Total transferred energy


1,80 m² 1,68 m² 201,79 kJ


Predicted total burn injury of the manikin

For this test, therefore, hands and feet are not included in the calculations.

First-degree burn injury area (%)	2nd degree burn injury area (%)	3rd-degree burn injury area (%)	Predicted total area of burn injury (2nd and 3rd degree) (%)
4,3	23,7	9,5	33,2



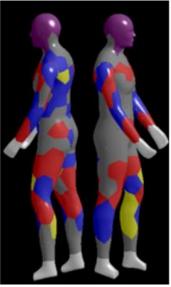



Sample nº 3 Ref.- 2024EP0609-S01_P1

Property	Measurement	Sample 3	Remark
Afterflame time	Video	0,9 s.	
Hole formation	Visual	Yes	
Melting	Visual	Yes	Labels
Embrittlement	Visual	Yes	
Smoke	Visual	Yes	
Dripping	Visual	No	
Shrinkage	Visual	Yes	
Functioning of garment accessories	Visual	Correct	

Heat Flux, Standard Deviation, Transferred Energy and Energy Transmission Factor per Body part

Sensor/temp.	Sample 3
Left arm – Heat Flux (kW/m²)	1,0
Left arm – Stdev (kW/m²)	0,3
Left arm – Transferred energy (kJ)	22,3
Left arm – Energy transmission factor	0,4
Right arm – Heat Flux (kW/m²)	1,0
Right arm – Stdev (kW/m²)	0,3
Right arm – Transferred energy (kJ)	20,5
Right arm – Energy transmission factor	0,3
Left Leg – Heat Flux (kW/m²)	1,0
Left Leg – Stdev (kW/m²)	0,3
Left Leg – Transferred energy (kJ)	48,5
Left Leg – Energy transmission factor	0,4
Right Leg – Heat Flux (kW/m²)	1,0
Right Leg – Stdev (kW/m²)	0,3
Right Leg – Transferred energy (kJ)	44,9
Right Leg – Energy transmission factor	0,3
Chest and abdomen – Heat Flux (kW/m²)	0,7
Chest and abdomen – Stdev (kW/m²)	0,3
Chest and abdomen – Transferred energy (kJ)	31,2
Chest and abdomen – Energy transmission factor	0,2
Back – Heat Flux (kW/m²)	0,8
Back – Stdev (kW/m²)	0,3
Back – Transferred energy (kJ)	29,6
Back – Energy transmission factor	0,3
Total energy transferred (kJ)	201,8
Total energy transmission factor	0,3


Sample before test nº 3 Ref.- 2024EP0609-S01_P1





Sample nº 3 Ref.- 2024EP0609-S01_P1

Clothed Burn Injury Over Time

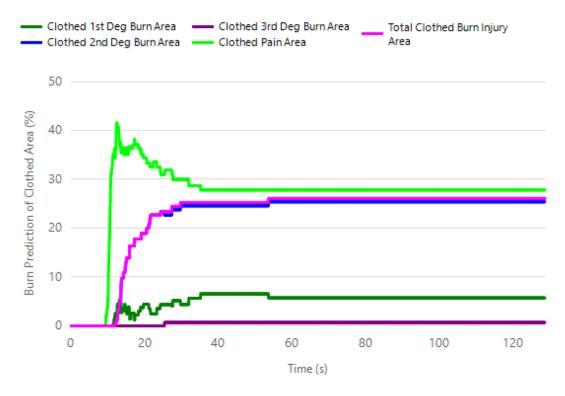

Sample after test nº 3 Ref.- 2024EP0609-S01_P1









Sample Ref.- 2024EP0609-S01_P1

Predicted burn injury on the total area of the manikin, except hands and feet.

Exposure	2nd degree burn injury area	3rd-degree burn injury area	Predicted total area of burn injury (2nd and 3rd degree)	Average	Standard deviation
1	23,3	6,7	30,0		
2	23,7	7,3	31,1	31,4	1,6
3	23,7	9,5	33,2		

Predicted burn injury on the total area of the manikin covered by the test specimen.

Exposure	2nd degree burn injury area	3rd-degree burn injury area	Predicted total area of burn injury (2nd and 3rd degree)	Average	Standard deviation
1	24,9	0,0	24,9		
2	25,4	0,7	26,1	26,5	1,8
3	25,4	3,0	28,4		

The test was carried out at laboratory located at Carretera Banyeres s/n - 03802 Alcoi, Alicante

Reference	Description
2024EP0609-S01_P1	After 1 wash cycle / Coverall



Lucia Martinez Head of PPE and Ballistics department



LIABILITY CLAUSES

- 1.- AITEX is liable only for the results of the methods of analysis used, as expressed in the report and referring exclusively to the materials or samples indicated in the same which are in its possession, the professional and legal liability of the Centre being limited to these. Unless otherwise stated, the samples were freely chosen and sent by the applicant.
- 2.- AITEX shall not be liable in any case of misuse of the test materials nor for undue interpretation or use of this document. AITEX laboratories do not carry out sampling.
- 3.- The Offer and / or Order to which the applicant gives approval through signature and seal, constitutes the Legally Executable Agreement in which AITEX is responsible for safeguarding and guaranteeing the absolute confidentiality of the management of all the information obtained or created during the performance of the contracted activities.
- 4.- In the eventuality of discrepancies between reports, a check to settle the same will be carried out in the head offices of AITEX. Also, the applicants undertake to notify AITEX of any complaint received by them as a result of the report, exempting this Centre from all liability if such is not done, the periods of conservation of the samples being taken into account.
- 5.- AITEX will provide at the request of the person concerned, the treatment of complaints procedure. In the event that you want to make it, direct it to: calidad@aitex.es.
- 6.- AITEX is not responsible for the information provided by customers, which is reflected in the Report, and may affect the validity of the results.
- 7.- AITEX is not responsible for an inadequate state of the sample received that could compromise the validity of the results, expressing such circumstance, in the test reports.
- 8.- AITEX may include in its reports, analyses, results, etc., any other evaluation which it considers necessary, even when it has not been specifically requested.
- 9.- When a Declaration of Conformity is requested, if not indicated otherwise, the decision rule according to ILAC-G8: 2009 will be applied with a security zone of 1U and a Probability of False Acceptance <2.5%.
- 10.- The uncertainties of tests, which are made explicit in the Results Report, have been estimated for a k = 2 (95% probability of coverage). If not informed, they are available to the client in AITEX.
- 11. The original materials and rests of samples, not subject to test, will be retained in AITEX during the twelve months following the issuance of the report, so that any check or claim which, in his case, wanted to make the applicant, should be exercised within the period indicated.
- 12.- This report may only be sent or delivered by hand to the applicant or to a person duly authorised by the same.
- 13.- The results of the tests and the statement of compliance with the specification in this report refer only to the test sample as it has been analyzed / tested and not the sample / item which has taken the test sample.
- 14.- The client must attend at all times, to the dates of the realization of the tests.
- 15.- According to Resolution EA (33) 31, the test reports must include the unique identification of the sample, and any brand or label of the manufacturer may be added. It is not allowed to re-issue test reports of untested sample names (references), they can only be re-issued for error correction or inclusion of omitted data that were already available at the time of the test. The laboratory can not assume responsibility for declaring that the product with the new trade name / trademark is strictly identical to the one originally tested; This responsibility belongs to the client.
- 16.- This report may not be partially reproduced without the written approval of the issuing laboratory.
- 17.- The tests have been carried out at the Alcoy plant with the address described on the first page of the report, unless another location is indicated in the results sheet of the specific test.