

Test Report

to

UL LLC POC: David Toshack 12 Laboratory Drive, Research Triangle Park, NC on

Characterization of Test Garments Using the PyroMan[™] System following NFPA 2112-2023 edition, section 8.5 Report # 2024-0131 Style GDI33

from

Textile Protection and Comfort Center (T-PACC)
College of Textiles
North Carolina State University
Raleigh, North Carolina 27695-8301

Issue Date: 1/31/2024

This report has been reviewed and authorized for release to the customer. This report meets all the requirement of ISO 17025 and the UL DAP. TL-785 takes responsibility for the information in this report.

Anthoney Shawn Deaton
Operations Director/ A. Shawn Deaton

02/03/2024

Date



Characterization of Test Garments Using the PyroManTM System: Report # 2024-0131 Style GDI33

UL LLC submitted coveralls and undergarments to the Textile Protection and Comfort Center (TPACC) in the Wilson College of Textiles at North Carolina State University. These garments were evaluated for a resistance to a simulated flash fire exposure outlined in NFPA 2112-2023 ed.: Standard on Flame-Resistant Garments for Protection of Industrial Personnel Against Short-Duration Thermal Exposures from Fire, section 8.5 in the TPACC Thermal Lab in Raleigh NC. This test evaluates the material of construction used in a standard coverall and does not apply to a garment design evaluation or an end-use garment evaluation. Any deviations from this standard were approved by the client prior to testing and are listed in Appendix A. The purpose of this report is to describe the testing system, test items and to present the results. This report shall not be reproduced except in full, without the approval of TPACC, to ensure parts of the report are not taken out of context.

NCSU PyroManTM Test System

The PyroManTM System consists of a number of components, designed to work together to measure the performance of protective clothing under full scale, flash fire exposure conditions. The most important requirements of this flash fire system are safe operation and reproducibility.

A list of all the equipment used for this testing along with the dates of calibration for the equipment that require calibration are stored internally on a North Carolina State University data storage system. This list can be provided to the client upon request.

A measurement uncertainty calculation was made for this system using 96 flame resistance garments. The measurement uncertainty was found to be 1.66% 2nd degree burn prediction or higher or this system.

Test Materials

UL LLC indicated ensembles were laundered prior to arrival. As garments are the test item, no sampling was required. Listed below is the sample ID and material description, as provided by UL LLC.

Sample ID Description

Style GDI33 93% Meta-Aramid/ 5% Para-Aramid/ 2% Antistatic,

Plain Weave, 4.5 osy, Color- Orange,

Test Results

Prior to testing, a nude manikin verification was done with a 3 seconds exposure. All test garments were evaluated with an average heat flux of $2.00 \text{ cal/cm}^2\text{sec} \pm 0.1 \text{ cal/cm}^2\text{sec}$ with a flash fire exposure of 3 seconds. In addition, at the end of each testing day another 3 second exposure is done to ensure the calibration did not drift significantly during the testing day. Test results for each test item are summarized in Table 1. Detailed data, including Pre/Post nude manikin

verifications, test data sheet, burn injury prediction graphic, and before and after pictures, are found in Appendix B. In addition, videos related to this test will be sent along with the report.

This report indicates that Style GDI33 produced an overall average predicted burn of 28.96%. This prediction was produced from a total of 122 sensors covering the entire surface of the manikin (excluding hands and feet) with each sensor being equally weighted. This report does not provide any interpretation of the results and cannot declare if a result is passing or failing. This report is only intended to report the data from the item tested. No test results were provided by an external provider.

<u>Caveat</u>: These data characterize the properties of materials or assemblies in response to radiant and convective energy under controlled laboratory conditions and should not be used to appraise the safety benefits or risk of materials, products, or assemblies under actual fire conditions. They are the results of specific laboratory exposures; extrapolations to other types of heat exposures or different combinations of radiant, convective and conductive assaults cannot be made. They are not presented to predict all types of field conditions where the nature of the thermal exposures can be physically complicated and unqualified. We wish to emphasize that it is not our intention to recommend, exclude, or predict the suitability of any commercial product for a particular end-use.

Table 1. Summary of Test Results

Burn (#)	NCSU File ID	Flame Exposure (sec)	Sample ID	Predicted Burn (%)		Breakopen		
				2nd	3rd	Overall	Yes	Max
							No	Length
								(cm)
1	240131K	3	Style GDI33, Rep #A-1	18.033	11.475	29.51	No	N/A
2	240131L	3	Style GDI33, Rep #A-2	18.033	10.656	28.69	No	N/A
3	240131M	3	Style GDI33, Rep #A-3	18.033	10.656	28.69	No	N/A
			AVERAGE	18.033	10.929	28.96		

Appendix A Agreed upon Deviations from NFPA 2112 and ASTM F1930-18

NFPA 2112

Section 8.5.3 – Washing Test specimens - This is completed by Underwriters Laboratories and assumed to meet the requirement but not verified. Since it cannot be verified it is listed as a deviation.

Section 8.5.8 – Pass/Fail - Being part of the North Carolina State University system we cannot identify an item as passing or failing. This will fall on the certification organization to determine.

ASTM F1930

Section 6.2.1 – Sensor Range - This section indicates that sensors must be able to have a range of 0 to 4.0 cal/s·cm². However, we cannot produce that amount of heat and we cannot find a source to verify that our sensors can achieve cal/s·cm².

Section 6.5.4.1 – Burn calculations without head burns included - This section requires calculating burn injury predictions for the entire manikin and the sections covered by a garment. NFPA 2112 supersedes this requirement by only requiring total burn injury predictions. Therefore, the predicted burn injury covered by just the garment is not reported.

Section 8.2.2 & 8.2.2.1 – Standard Garment - This is completed by Underwriters Laboratories and assumed to meet the requirement but not verified. Since it cannot be verified it is listed as a deviation.

Section 9.3 – Area Density Measurements - This is completed by Underwriters Laboratories and assumed to meet the requirement but not verified. Since it cannot be verified it is listed as a deviation.

Section 13.5.1.3 – Burn Predictions and Variation Statistic – Burn injury predictions are provided however variation statistics requirements are not defined. Therefore, we do not provide variation statistics.

Section 13.5.2 – Burn Prediction covered by garment – NFPA 2112 requires total burn injury predictions, therefore we only report total burn injury predictions for the entire manikin.

Section 13.6.1 – Afterflame intensity, location, and duration – Due to the complexity of detailing all this information in a few seconds time frame we only record the overall afterflame duration. If afterflame is extreme or located in one particular spot on the garment, these observations will be noted.

Appendix B

Pre/Post Nude Verification Results,
PyroManTM Test Specifications, Test Remarks, Photos, and
Manikin Burn Injury Prediction

Data File Name	240131K	Test Date	2024-01-31 9:03 AM	
System Identification	PyroMan™	Sponsor	UL	
Garment Identification	STYLE GDI33 COVERALL, REP# A-1			
Garment size	NFPA 2112 REFERENCE		Conditioning Room Removal Time	2024-01-31 08:56 AM
N Washes	1 (-1 = Unknown) 🗸 100	0% Cotton Underwear &		
Comments	LAYER 1: COTTON T-SHIRT AND BRIEF LAYER 2: STYLE GDI33 COVERALL, 93% META-ARAMID/ 5% PARA-ARAMID/ 2% ANTISTATIC, PLAIN WEAVE, 4.5 OSY, COLOR-ORANGE COVERALLS PLACED IN CONDITIONING ROOM: 01/29/2024 AT 1:00 PM			
	GARMENTS WERE PRECONDITIONED BY UL, CONDITIONED BY NCSU GARMENTS STORED IN CONDITIONED SPACE PRIOR TO TESTING TESTING CONDUCTED ACCORDING TO NFPA 2112-2023 AND ASTM F1930-18 BY SR THERMAL PROTECTION SCIENTIST JOHN MORTON-ASLANIS AND RESEARCH TECHNICIAN MARK MARTIN UL PROJECT ENGINEER: DAVID TOSHACK, DAVID.TOSHACK@UL.COM UL PROJECT#4790794697, UL CUSTOMER NAME: G D INTERNATIONAL CONDITIONING ROOM TEMP: 21°C, CONDITIONING ROOM HUMIDITY: 66% (AT TIME OF COVERALL REMOVAL)			
Post Test Comments	AFTERFLAME NOT RECORDED			
	mage Broak spen	orittlement N/A	Start Roo	om Temp (oC) 22 as. Temp (oC) 31
Emoke Generation Shrin Light Total DAQ time Exposure Time	Severe None (s) 61 Avg Expos. Heat Flux	N/A	Start Avg Ser	, ,

% 2nd Degree Burns 18.033 % Total Burn 29.51

For More Information Contact:

North Carolina State University College of Textiles Textile Protection and Comfort Center 1020 Main Campus Drive Raleigh, NC 27606

END of Thermal Protective Clothing Analysis Sheet


Style GDI33 Coverall, Rep# A-1 240131K






Style GDI33 Coverall, Rep# A-1 240131K



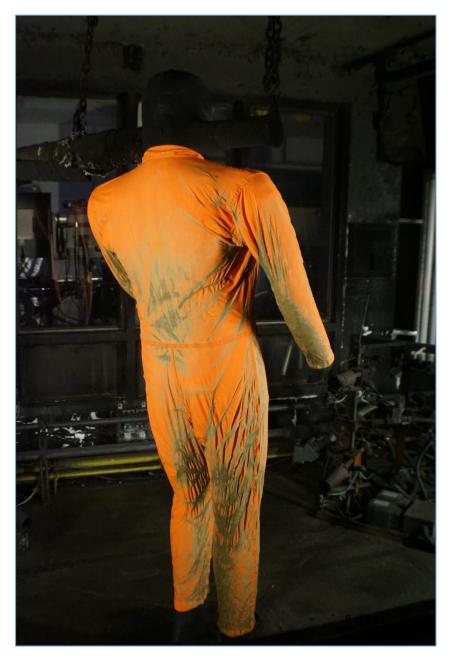

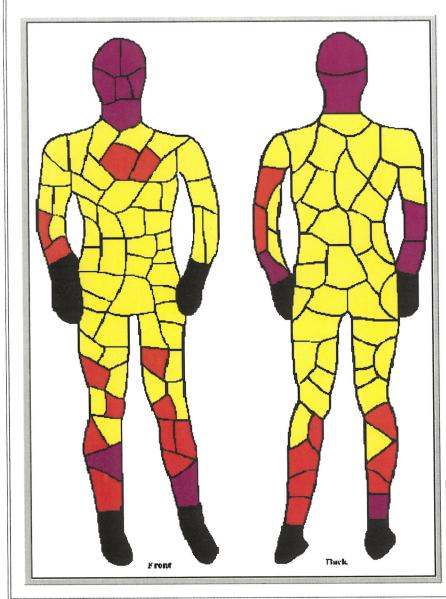

NCSU

PyroMan™

3-Layer Skin Model

Thermal Protective Clothing Analysis System


Burn Injury Prediction

UL	
STYLE GDI33 COVERALL, REP# A-1	
Exposure Time (s) 3.00 DAQ Time (s) 61.00 Time Step (s) 0.10	
% 2nd Degree Burns 18.033 % Total Burn 29.51	
Burn Calculation Time (s) 60.8	
Invalid Sensor	
No Burn	
2nd Degree Burn	
3rd Degree Burn 240131	K

PyroMan™

Thermal Protective Clothing Analysis System

3-Layer Skin Model

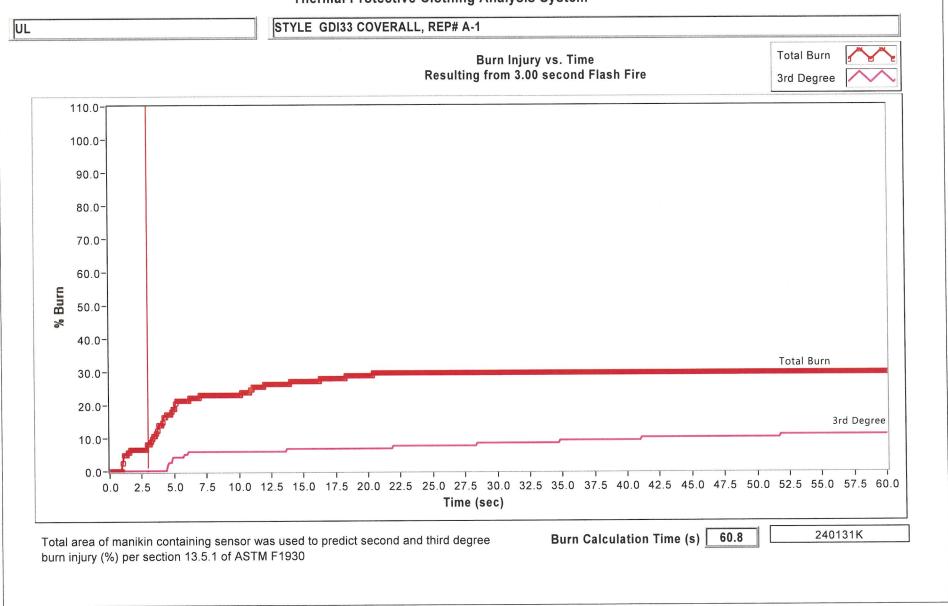

Thermal Protective Clothing Analysis

Data File Nam	e 240131L	Test Date	2024-01-31 9:15 AM	
System Identification	PyroMan™	Sponsor	UL	
Garment Identification	STYLE GDI33 COVERALL, REP# A-2			
Garment size	NFPA 2112 REFERENCE		Conditioning Room Removal Time	2024-01-31 09:09 AM
N Washes	1 (-1 = Unknown) 📝 10	00% Cotton Underwear		
Garment/Fabric Comments	LAYER 1: COTTON T-SHIRT AND BRIE LAYER 2: STYLE GDI33 COVERALL, 9 4.5 OSY, COLOR-ORANGE COVERALLS PLACED IN CONDITIONII	93% META-ARAMID/ 5%		NTISTATIC, PLAIN WEAVE,
Pre Test Comments	GARMENTS WERE PRECONDITIONED BY UL, CONDITIONED BY NCSU GARMENTS STORED IN CONDITIONED SPACE PRIOR TO TESTING TESTING CONDUCTED ACCORDING TO NFPA 2112-2023 AND ASTM F1930-18 BY SR THERMAL PROTECTION SCIENTIST JOHN MORTON-ASLANIS AND RESEARCH TECHNICIAN MARK MARTIN UL PROJECT ENGINEER: DAVID TOSHACK, DAVID.TOSHACK@UL.COM UL PROJECT#4790794697, UL CUSTOMER NAME: G D INTERNATIONAL CONDITIONING ROOM TEMP: 21°C, CONDITIONING ROOM HUMIDITY: 66% (AT TIME OF COVERALL REMOVAL)			
Post Test Comments	AFTERFLAME NOT RECORDED			
Smoke Generation Shi	rinkage Break-Open En	nbrittlement	Start Roo	om Temp (oC) 21
Light 🔽	Severe None	N/A	Start Avg Sen	s. Temp (oC) 31
Total DAQ time (s) 61 Avg Expos. Heat Flux (cal/(cm^2*sec) 2.00 Scan Interval (s) 0.10			nterval (s) 0.10	
Exposure Time	e (s) 3.00 Toro	ches Used ALL	ALL, or those	e used, separated by commas
			Burn Calculation	Time (s) 60.8

% 2nd Degree Burns 18.033 % Total Burn 28.69

For More Information Contact:

North Carolina State University College of Textiles Textile Protection and Comfort Center 1020 Main Campus Drive Raleigh, NC 27606

END of Thermal Protective Clothing Analysis Sheet


Style GDI33 Coverall, Rep# A-2 240131L






Style GDI33 Coverall, Rep# A-2 240131L



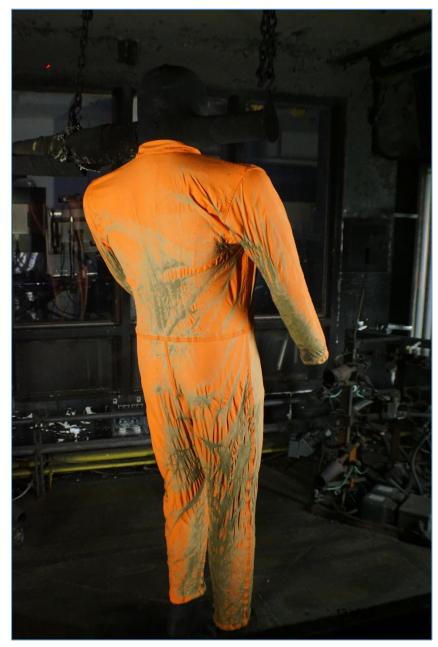

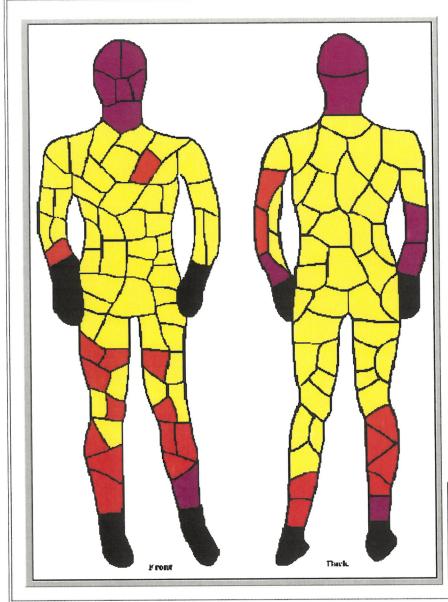

NCSU

PyroMan™

3-Layer Skin Model

Thermal Protective Clothing Analysis System


Burn Injury Prediction

UL					
STYLE GDI33 COVERALL, REP# A-2					
Exposure Time (s) 3.00 DAQ Time (s) 61.00 Time Step (s) 0.10					
% 2nd Degree Burns 18.033 % Total Burn 28.69					
Burn Calculation Time (s) 60.8					
Invalid Sensor					
No Burn					
2nd Degree Burn					
3rd Degree Burn 240131L					

PyroMan™

Thermal Protective Clothing Analysis System

3-Layer Skin Model

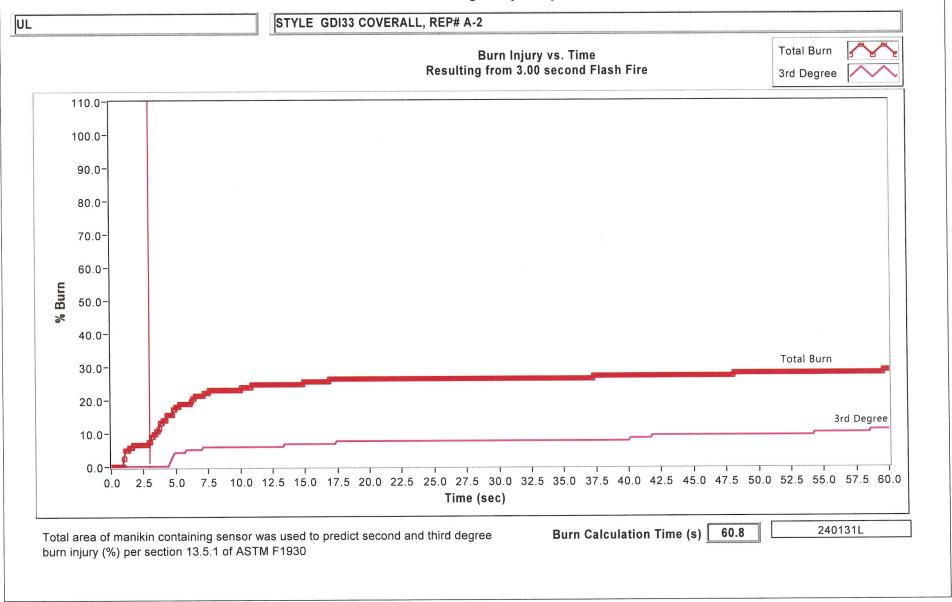

Thermal Protective Clothing Analysis

Data File Nam	240131M	Test Date	2024-01-31 9:26 AM	
System Identification	PyroMan™	Sponsor	UL	
Garment Identification	STYLE GDI33 COVERALL, REP# A-3			
Garment size	NFPA 2112 REFERENCE		Conditioning Room Removal Time	2024-01-31 09:20 AM
N Washes	1 (-1 = Unknown) 🗸 1	00% Cotton Underwear 8	& Tshirt	1
Garment/Fabric Comments	LAYER 1: COTTON T-SHIRT AND BRIEF LAYER 2: STYLE GDI33 COVERALL, 93% META-ARAMID/ 5% PARA-ARAMID/ 2% ANTISTATIC, PLAIN WEAVE, 4.5 OSY, COLOR-ORANGE COVERALLS PLACED IN CONDITIONING ROOM: 01/29/2024 AT 1:00 PM			
Pre Test Comments	GARMENTS WERE PRECONDITIONED BY UL, CONDITIONED BY NCSU GARMENTS STORED IN CONDITIONED SPACE PRIOR TO TESTING TESTING CONDUCTED ACCORDING TO NFPA 2112-2023 AND ASTM F1930-18 BY SR THERMAL PROTECTION SCIENTIST JOHN MORTON-ASLANIS AND RESEARCH TECHNICIAN MARK MARTIN UL PROJECT ENGINEER: DAVID TOSHACK, DAVID TOSHACK@UL COM UL PROJECT#4790794697, UL CUSTOMER NAME: G D INTERNATIONAL CONDITIONING ROOM TEMP: 21°C, CONDITIONING ROOM HUMIDITY: 66% (AT TIME OF COVERALL REMOVAL)			
Post Test Comments Smoke Generation Shi	rinkage Break-Open Er	nbrittlement N/A	named and a second	om Temp (oC) 22 ns. Temp (oC) 32
Total DAQ tim	e (s) 61 Avg Expos. Heat Fl		2.00 Scan I	interval (s) 0.10 se used, separated by commas
			Burn Calculation	1 Time (s) 60.8

 % 2nd Degree Burns
 18.033
 % Total Burn
 28.69

 % 3rd Degree Burns
 10.656

For More Information Contact:

North Carolina State University
College of Textiles
Textile Protection and Comfort Center
1020 Main Campus Drive
Raleigh, NC 27606

END of Thermal Protective Clothing Analysis Sheet


Style GDI33 Coverall, Rep# A-3 240131M






Style GDI33 Coverall, Rep# A-3 240131M



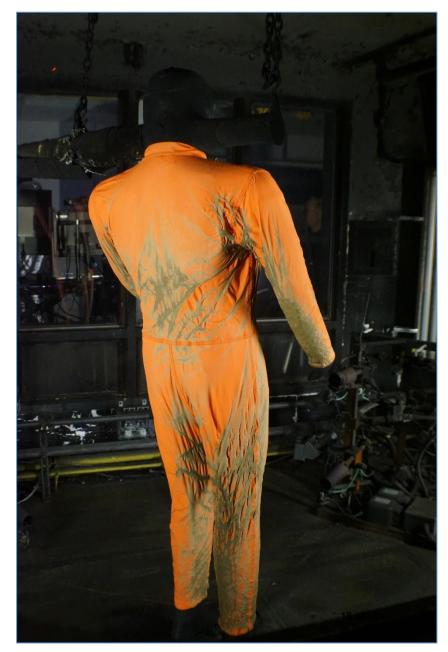

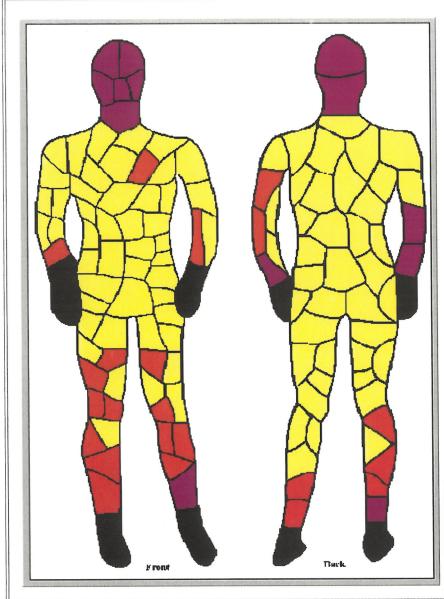

NCSU

PyroMan™

3-Layer Skin Model

Thermal Protective Clothing Analysis System


Burn Injury Prediction

UL					
STYLE GDI33 COVERALL, REP# A-3					
Exposure Time (s) 3.00 DAQ Time (s) 61.00 Time Step (s) 0.10					
% 2nd Degree Burns 18.033 % Total Burn 28.69					
Burn Calculation Time (s) 60.8					
Invalid Sensor					
No Burn					
2nd Degree Burn					
3rd Degree Burn 240131M					

PyroMan™

Thermal Protective Clothing Analysis System

3-Layer Skin Model

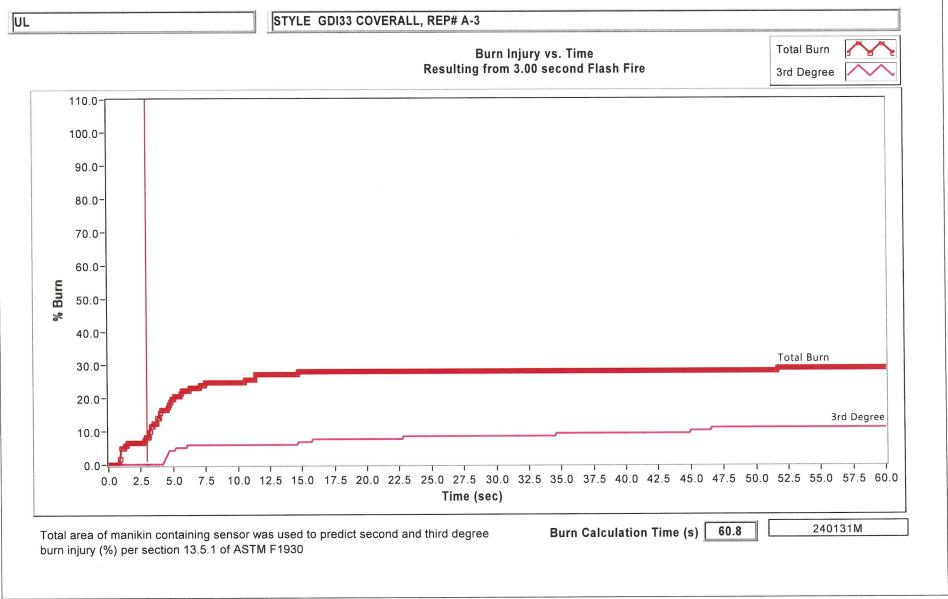

Date Printed: Printed on 01/31/2024 07:25:10 AM Data Directory: C:\Users\PyroMan-1\Documents\TPACC\PyroMan\data\240131D Data File: 240131D.dat Exposure Time (s): 3.0 Time Interval (s): 0.10 Sensor Flux Avg (cal/cm^2/s): 2.04 Sensor Flux SD (cal/cm^2/s): 0.42

For More Information Contact:

North Carolina State University College of Textiles Textile Protection and Comfort Center 1020 Main Campus Drive Raleigh, NC 27606

Start of Day Calibration

Date Printed: Printed on 01/31/2024 10:20:35 AM Data Directory: C:\Users\PyroMan-1\Documents\TPACC\PyroMan\data\240131Q Data File: 240131Q.dat Exposure Time (s): 3.0 Time Interval (s): 0.10 Sensor Flux Avg (cal/cm^2/s): 2.04 Sensor Flux SD (cal/cm^2/s): 0.38

For More Information Contact:

North Carolina State University
College of Textiles
Textile Protection and Comfort Center
1020 Main Campus Drive
Raleigh, NC 27606

End of Day Calibration